

## THE INHIBITION OF 304SS IN HYDROCHLORIC ACID SOLUTION BY *CERA ALBA* EXTRACT

WAHYONO SUPRAPTO, RUDY SOENOKO,  
AGUS SUPRAPTO, FEMIANA GAPSARI\*

Mechanical Engineering, Faculty of Engineering, Brawijaya University  
MT.Haryono 110 Malang, Indonesia

\*Corresponding Author: femianagapsari@gmail.com

### Abstract

Organic inhibitors became popular for protection against corrosion especially in acid solution in acid to prevent metal dissolution. Hydrochloric acid is widely used in the pickling, cleaning, and descaling process of metals. The high performance of corrosion inhibition efficiency of *Cera alba*(CA) extract was investigated for 304SS corrosion in 1Mhydrochloric acid using polarizationpotentodynamic method. The extract of CA was characterized by Fourier Transform Infrared Spectroscopy (FTIR). The polarization study indicated that the formulations act as mixed-type inhibitor. The adsorption process on 304SS followed Frumkin isotherm. The associated activation parameters and the thermodynamics data of adsorption were evaluated and discussed. The adsorbed film formed on the metal surfaced was characterized byScanning Electron Microscope (SEM).

Keywords: Cera alba, EIS, FTIR, Inhibitor, Polarization.

### 1.Introduction

Stainless steel type 304 is the most common form of stainless steel used in many industrial applications involving in tank production and other appliances connected to chemical material, petrochemical, paper, pollution control, hydrometallurgy and petroleum industry. In several producing activities at high temperature, some companies begin to use 304SS. It is reccomended to use in furnaces, refinery petrochemical, super heater, hanger tubes, radiant tubes, anchors refractory, dampers, inner tubes, lifters, expansion bellow, furnace fan, muffle, and bell furnaces. Corrosion of metals in aggressive solutions is an important problem in industrial cleaning and pretreatment processes such as acid

<b>Nomenclatures</b>	
<i>A</i>	Arrhenius
<i>C</i>	Concentration of inhibitor, g/L
<i>CR</i>	Corrosion rate, mmpy
<i>E<sub>a</sub></i>	Activation energy, kJ/mol
<i>E<sub>corr</sub></i>	Corrosion potential, V
<i>h</i>	Planck's constant
<i>I<sub>cor</sub></i>	Corrosion current density of absence inhibitor, A/cm <sup>2</sup>
<i>I<sub>cor(i)</sub></i>	Corrosion current density of presence inhibitor, A/cm <sup>2</sup>
<i>IE</i>	Inhibition efficiency, %
<i>K<sub>ads</sub></i>	Adsorption equilibrium constant
<i>N</i>	Avogadro's number
<i>R</i>	The universal gas constant
<i>R<sup>2</sup></i>	Coefficient of determination
<i>T</i>	Temperature, K
<b>Greek Symbols</b>	
<i>α</i>	interaction parameter
<i>β<sub>a</sub></i>	Cathodic tafel slopes, V/dec
<i>β<sub>c</sub></i>	Anodic tafel slopes, V/dec
<i>ΔS</i>	Entropy, J/mol.K
<i>ΔG<sub>ads</sub></i>	Free energy of adsorption, kJ/mol
<i>ΔH</i>	Entalpy, kJ/mol
<i>θ</i>	Degree of surface coverage
<b>Abbreviations</b>	
AR	Acid Reagent
ASTM	The American Society for Testing and Materials
ads	Adsorption
CA	Cera Alba
CE	Counter Electrode
FEI	Field Electron and Ion
FTIR	Fourier Transform Infrared
HCl	Hydrochloric Acid
OCP	Open Circuit Potential
RE	Reference Electrode
SEM	Scanning Electron Microscope
SS	Stainless Steel
WE	Working Electrode

pickling, industrial acid cleaning, acid descaling and oil well acidizing. Corrosion inhibitor is a popular method to prevent and protect corrosion rate of metal surfaces which are in an acidic environment. [1, 2]. By adding small concentration of these materials to corrosive environments, will prevent the reaction of metal with media[3-7]. Inhibitors reduce the corrosion rate by changing the anodic or cathodic reaction, reducing diffusion rate of reactants into the metal surface [8]. The inhibitors are derived from inorganic and organic compound in which aninorganic compound isexpensive and not environmentally friendly [9, 10]. Therefore, the study of new non toxic inhibitors is important to solve this problem. The study of organic corrosion inhibition is an alternative

field of research due to its usefulness in various industries. These compounds act as good inhibitors due to their heteroatom structures such as sulfur, nitrogen and oxygen [11, 12].

Some research on organic inhibitor in hydrochloric acid have been studied [2, 13-19]. Nonetheless, there is still a need for research on other organic compounds can be used as inhibitors in industrial applications.

This present work therefore introduces Cera Alba (CA) extract as a novel green inhibitor for 304 SS in hydrochloric acid. CA is a natural wax produced by honey bees. CA is used to store honey, royal jelly, and propolis. Honey is a natural material that has been reported good for retarding the corrosion rate of various metal [20-23]. The same with propolis [24, 25]. The objective of this study was to investigate the effect of CA extract as corrosion inhibitors for 304SS in M HCl. Potentiodynamic polarization method were utilized, and adsorption isotherms and thermodynamic parameters were calculated and discussed.

## **2. Experimental Method**

Experimental method is begun by preparing the metal specimen and the inhibitor. Later, the extraction from the next inhibitor is characterized. The aim is to find out the content of the inhibitor. Next, the inhibitor is added to the solution which has been prepared before the electrochemical test.

### **2.1. Preparation of specimens**

The experimet were performed with 304SS with the following composition (wt %): 0.04%C, 0.52 % Si, 0.92 % Mn, 0.030% P, 0.002 % S, 9.58% Ni, 18.15 % Cr, Bal.Fe. Density of 304SS was 7.9 g/cm<sup>3</sup> The 304SS was added to epoxy resin with a geometric exposed surface area measuring 1 cm<sup>2</sup> and connected to the electrolyte. The 304SS were polished consecutively with emery paper of from 500 to 1500 grades. The specimen were washed with distilled water, rinsed in ethanol, degreased with acetobe and finally dried.

### **2.2. Inhibitor preparation**

CA used was obtained from Malang, Indonesia. The CA was extracted by solid-liquid method in order to obtain the optimum conditions. Half of CA powder was extracted by maceration method using 99% ethanol (Merck). 200 g of CA was extracted with 200 ml of ethanol. The ethanol was evaporated by using a water bath.

### **2.3. Inhibitor characterization**

FTIR analysis of CA extract was used to determine the functional groups. Infrared spectra were recorded in Shimadzu IR Prestige-21, FTIR spectrometer. This spectrometer using KBr-disc techniques. The region between 4000-400 cm<sup>-1</sup> with resolution of 2 cm<sup>-1</sup>.

## 2.4. Solution preparation

The corrosive media of 1 M HCl was prepared by dilution of AR grade 37% HCl (Merck) using distilled water. HCl was used as corrosive media to explore potential inhibition of CA extract.

## 2.5. Electrochemical measurement

Corrosion testing conducted based on standards ASTM (the American Society for Testing and Materials) G-31 [18] (ASTM). To know kinetic of corrosion process polarization potentiodynamic were used. Independent variables used in this study were 0, 1, 2, 3, and 4 g / L CA extract concentration. In this case, the room temperature was set at 25<sup>0</sup>C and the electrochemical measurements were performed with the Autolab PGSTAT 128N. A-three-electrode system was used to perform electrochemical tests which include 304SS as working electrode (WE), Ag/AgCl (KCl 3 M) as reference electrode (RE), and platinum as counter electrode (CE). Three electrodes immersed in a batch for 2 hours.

The starting potential was -0.1 V and the scan rate range extended up +0.1 V at Open Circuit Potential (OCP) with voltage scan rate of 0.001 V/s. Inhibition efficiency calculated by Eq. 1 [26, 27]:

$$IE (\%) = \frac{I_{corr} - I_{corr(i)}}{I_{corr}} \times 100 \% \quad (1)$$

where,  $I_{corr}$  and  $I_{corr(i)}$  is corrosion current density in case of absence and presence inhibitor.

## 2.6. Scanning electron microscope (SEM)

SEM type FEI, inspect type -S50 was employed to analyzed surface morphology of 304SS at various concentration of inhibitor. The 304SS specimens was prepared as described at section 2.1.

## 3. Result and Discussion

The result of the experiment test will be analyzed in detail in this section. The result of CA extract characteristic can be seen from the result of FTIR. The corrosion rate and efficiency inhibition are displayed on Fig. 1 and Table 1.

### 3.1. Fourier transform infrared spectroscopy (FTIR)

FTIR testing results showed some absorption spectrum with strong intensity. The strong absorption band at 3369.41 cm<sup>-1</sup> is attributed to O-H. Wave number 2925.81 cm<sup>-1</sup> is related to C-H. a carbonyl group (C=O, ketone) at 1714.6 cm<sup>-1</sup>. Aromatic group at 1618.17 cm<sup>-1</sup> and 1454.23 cm<sup>-1</sup>. The absorption band at 1454.23 cm<sup>-1</sup> is related to C-H. As well as the wavenumber 1049.20 cm<sup>-1</sup> as the absorption of the alcohol functional group C-O. The result implies that CA extract have flavanoids content.

### 3.2. Potentiodynamic polarization method

Potentiodynamic polarization method aims to determine the effect of extracts CA inhibition and types of inhibitor. Tafel plot of 304SS in HCl media with various concentrations of inhibitors shown in Fig. 1. The IE (%) was calculated using the Eq. (1). The electrochemical parameters obtained from the polarization measurements are listed in Table 1.

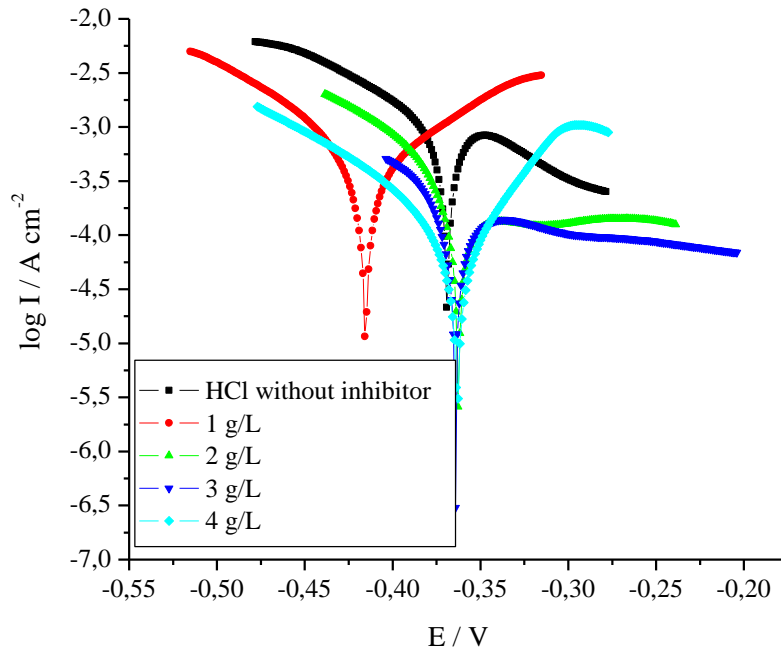


Fig. 1. Tafel plots with various concentration of CA extract.

Table 1. Tafel extrapolation of 304SS in 1M HCl in various concentration of CA extract.


Inhibitor (g/L)	$\beta_a$ (V/dec)	$\beta_c$ (V/dec)	$E_{corr}$ (V)	$I_{corr}$ ( $A/cm^2$ )	CR (mmpy)	IE (%)
0	0.086	-0.5171	-0.37	$2.90 \times 10^{-3}$	30.17	-
1	0.179	-7.844	-0.42	$2.33 \times 10^{-3}$	24.26	19.6
2	0.052	-0.10	-0.36	$6.55 \times 10^{-4}$	6.88	77.42
3	0.071	-0.116	-0.33	$2.80 \times 10^{-4}$	2.91	90.34
4	0.072	0.658	-0.36	$9.63 \times 10^{-7}$	1.001	99.96

Polarization measurement results as shown in Table 1 indicate the effect of CA extract to corrosion inhibition on 304SS in hydrochloric acid. The addition of CA extract cause current density decreased. The inhibition of both anodic and cathodic reactions is increasingly pronounced when increasing CA extract concentration. Inhibitors indicated anodic or cathodic type when corrosion potential shifted more than 85 mV of the corrosion potential absence inhibitor [28].  $E_{corr}$  shifted less than 85 mV as shown in Table 1 (polarization). It can be classified as the mixed type corrosion inhibitor. The Tafel plots show that the presence of the extract caused a decrease in both the anodic and cathodic

current densities. CA. The addition of CA extract to the HCl solution reduces the anodic dissolution of iron and also retards the cathodic hydrogen evolution reactions as would be expected. Both corrosion current density and corrosion rate were considerably reduced in the presence of the extract. These results are indicative of the adsorption of inhibitor molecules on 304SS surface [29]. The cathodic ( $\beta_c$ ) and anodic Tafel slopes ( $\beta_a$ ) did not significantly change with the addition of the CA extract. Irregularity of  $\beta_a$  and  $\beta_c$  showed that the CA extract was a mixed inhibitors modify the mechanism of anodic dissolution and cathodic hydrogen evolution [30, 31]. The highest inhibitor efficiency (99.95%) was obtained by adding 4 g/LCA of extract.

### 3.3. Temperature effect and activation energy

In order to study the effect of temperature 304SS surface of the inhibitor in 1 M HCl solution, polarization potentiodynamic were studied in the temperature range of 298-328 K in the absence and presence of CA extract shown in Fig. 2.

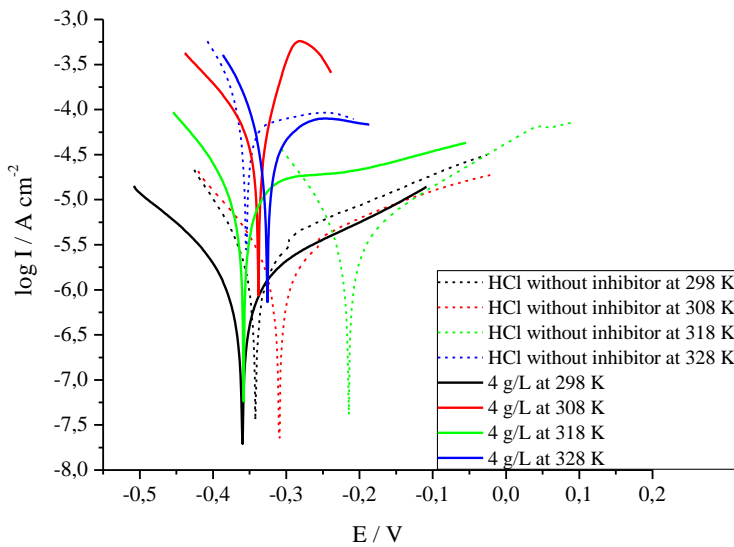

**Fig. 2. Polarization curve of 304SS in the hydrochloric acid 1 M absence and presence inhibitor at varied temperature.**

Table 2 shows efficiency inhibition decreases with increasing temperature. It may be due to that the higher temperature might cause the desorption of the CA extract from the steel surface [32]. IE decrease with increasing temperature caused physisorption on metal surfaces [33]. Physisorption showed the ability of dipoles interactions is relatively weak and at high temperature could cause desorption of BWP extract from the metal surface [34].


The effect of temperature towards the corrosion rate can be declared as Arrhenius equation, Eq. 2. Temperature is essential parameter in studies on metal dissolution. The temperature can modify the interaction between the steel electrode and the acidic media [2]. The value of  $E_a$  can be obtained from the slope of linear regression result between  $\ln I_{corr}$  and  $1/T$  (Fig. 3). The calculation result of  $E_a$  value with inhibitor is bigger than without inhibitor (Table 3). The increase of

$E_a$  value with inhibitor shows that reaction occurs slowly and its corrosion rate is sensitive to temperature [35]. High value of  $E_a$  will lower the corrosion rate or lower the corrosion current density. This indicates that the electron transfer in oxidation-reduction process will become less dense and hence it will lower the corrosion rate [13].

**Table 2.**The potentiodynamic polarization data of 304 SS in the hydrochloric acid 1M absence and presence inhibitor at temperature variations.

Inhibitor (g/L)	T (K)	$\beta_a$ (V/dec)	$\beta_c$ (V/dec)	$E_{corr}$ (V)	$I_{corr}$ (A/cm <sup>2</sup> )	IE%
0	298	0.043	0.078	-0.33	$9.83 \times 10^{-7}$	-
	308	0.079	0.137	-0.31	$1.60 \times 10^{-6}$	-
	318	0.095	0.43	-0.21	$5.29 \times 10^{-6}$	-
	328	0.064	-0.21	-0.38	$6.34 \times 10^{-4}$	-
4	298	0.032	0.036	-0.37	$2.29 \times 10^{-8}$	97.67
	308	0.081	0.039	-0.34	$4.11 \times 10^{-7}$	74.31
	318	0.046	0.079	-0.35	$3.67 \times 10^{-6}$	30.62
	328	0.074	0.413	-0.37	$5.56 \times 10^{-4}$	12.30

Arrhenius equation :  $\ln i_{corr} = \ln A - \frac{E_a}{R} \left(\frac{1}{T}\right)$  (2)

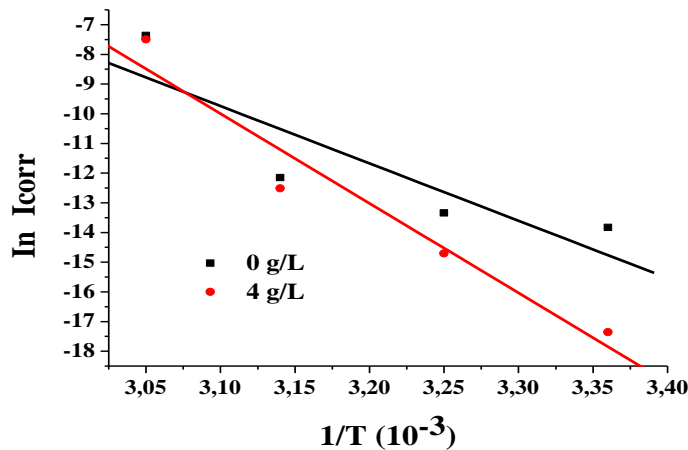

**Fig. 3.** Arrhennius plot of 304SS in 1M M HClwith and without inhibitor.

**Table 3.** Activation energy value.

Concentration of extract CA (g/L)	$E_a$ (kJ/mol)
0	161.83
4	246.80

### 3.4. Adsorption isotherm and thermodynamic calculation

In order to know the mechanism of adsorption, the isothermal adsorption is calculated. Beside the calculation of the isothermal adsorption, thermodynamical calculation must be conducted to gain supporting data of spontaneous corrosion, entaly and entropy as the influence of CA extract addition to the solution.

#### 3.4.1. Adsorption isotherm of CA extract

The adsorption behaviour of the inhibitor on the metal surface reveal the mechanism of corrosion inhibition. In this study, the data were tested graphically by fitting to various adsorption isotherms including the Freundlich, Temkin, Florry-Huggins, Langmuir, ang Frumkin Isotherms. The best fit isotherm followed Frumkin isotherm, Eq. 3. The value of  $E_a$  is presented in Table 3 and Fig. 4. These results indicate that the adsorption isotherm of CA extracts CA physisorption which according to the potentiodynamic polarization data.

$$\log \left\{ \frac{\theta}{(1-\theta)C} \right\} = \log K_{ads} + a\theta \quad (3)$$

where,  $C$  is the concentration of inhibitor,  $\theta$  is the degree of surface coverage,  $K_{ads}$  is the adsorption equilibrium constant and  $a$  is an interaction parameter. The value of  $a$  takes into account and means the attraction ( $a > 0$ ) or repulsion ( $a < 0$ ) between adsorbed species. When  $a = 0$  indicate no interaction and this isotherm becomes equivalent to Langmuir isotherm.

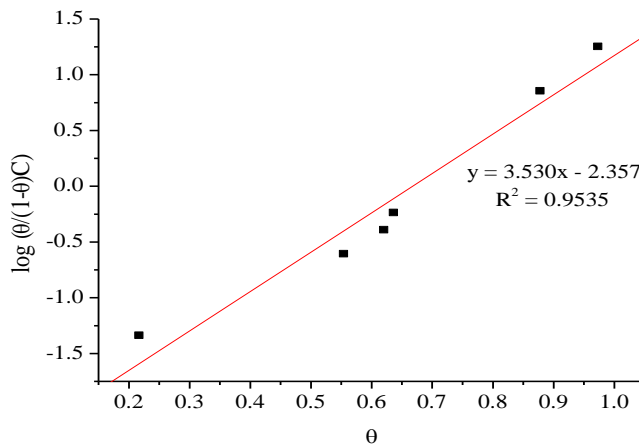


Fig. 4. Frumkin isothermal adsorption.

#### 3.4.2. Thermodynamic calculation

The value of  $K_{ads}$  is related to the free energy of adsorption by the Eq. (4).

$$K_{ads} = \frac{1}{55.5} \exp \left( \frac{-\Delta G_{ads}^{\circ}}{RT} \right) \quad (4)$$

where,  $\Delta G_{ads}^{\circ}$  is standard free energy of adsorption and the value of 55.5 is the concentration of water in solution expressed in mol. The calculated  $\Delta G_{ads}^{\circ}$  are given in Table 4. Generally, values of  $\Delta G_{ads}^{\circ}$  up to -20 kJ/mol are consistent with electrostatic interaction between charged molecules and a charged metal



(physisorption). While those around -40 kJ/mol involves charge sharing or transfer from the inhibitor molecules to the metal surface to form a co-ordinate type of bond (chemisorption) [36]. The  $\Delta G_{ads}^{\circ}$  value in this study (Table 4) indicates that CAextract adsorbed via physisorption on the 304SS surface both in 1 M HCl solution. The negative values for  $\Delta G_{ads}^{\circ}$  indicate spontaneous adsorption of CAextract [37]. This result support that adsorption of CA extract is physisorption and that in a good agreement with the explanation in section 3.2.

The change of enthalpy ( $\Delta H^{\circ}$ ) and entropy ( $\Delta S^{\circ}$ ) of activation calculated by the *slope* and *intercept* in linier plot shown in Fig. 3 and Eq. 5 [38].

$$I_{corr} = \left(\frac{RT}{Nh}\right) \exp\left(\frac{\Delta S^{\circ}}{R}\right) \exp\left(\frac{-\Delta H^{\circ}}{R}\right) \quad (5)$$


where, *h* is Planck's constant, N is the Avogadro's number, T is absolute temperature, and R is the universal gas constant. The  $\Delta H^{\circ}$  value and  $\Delta S^{\circ}$  value is presented in Table 4. The positive values of  $\Delta H^{\circ}$  both in with and without CA extract reflect the endothermic nature of steel dissolution [32, 37]. The positive value of  $\Delta S^{\circ}$  showed that adsorption process followed with an increase  $\Delta S^{\circ}$ , which is the driving force for adsorption inhibitor to the metal surface [38].

**Table 4. Thermodynamic parameters for 304 SS in 1M HCl with and without inhibitor.**

Inhibitor (g/L)	$\Delta G_{ads}^{\circ}$ (kJ/mol)	$\Delta H^{\circ}$ (kJ/mol)	$\Delta S^{\circ}$ (J/mol.K)
0	-	159.01	196.28
4	-12.26	243.87	456.47

### 3.5. Surface morphology

Surface analysis using scanning electron microscope (SEM) proved a significant improvement on surface morphology of 304SS plates in the addition of CA extract. Figure 5 shows surface morphology of 304SS in HCl with and without inhibitor.

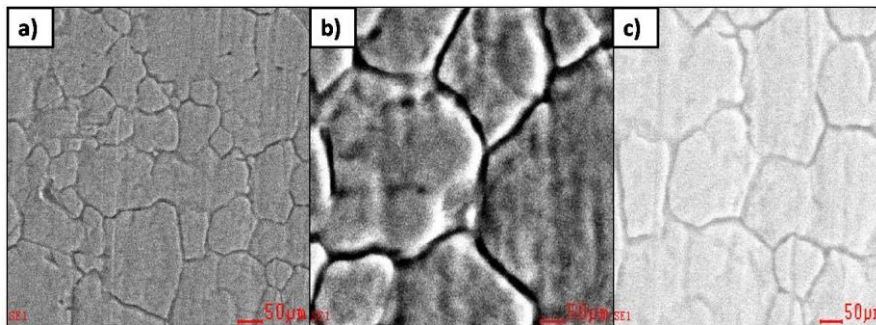

**Fig. 5. Micro photograph obtained by SEM for surface morphology of 304SS before corrosion (a), after corrosion in 1 M HCl without inhibitor (b) and after corrosion in 1 M HCl with inhibitor (c).**

The SEM provides means of surface morphology. Fig. 5(a) shows clearly in the surface before immersion smooth and uniform. When sample was immersed

in HCl, corrosion pits were created on the surface due to aggressive attack of acid Fig. 5(b). It was indicates deposition of corrosion products. The addition of inhibitor retarded the corrosion rate and formed smooth layer Fig. 5(c). Brightness of the image indicates good interaction of inhibitor with 304SS surface.

### 3.6. Inhibition mechanism

The corrosion of 304SS in HCl solution retarded with addition on inhibitor. Based on the polarization measurement, the decrease of IE percentage with the increase of temperature indicates to occur physical adsorption by inhibitor at 304SS surface. Polarization potentiodynamic measurements showed the CA extract retarded corrosion rate which corresponds to molecular adsorption of inhibitor. These organic compound protonated in HCL solution which favored adsorption of these molecules over surface of negatively charged 304SS(electrostatic bonding). In this research adsorbed inhibitor molecules accumulated at the metal/ acid interface and constructed layer surrounding 304SS.

### 4. Conclusion

CA extract as good inhibitor on 304SS in 1M HCl. It can inhibit corrosion process. The value of inhibition efficiency obtained is 99.96% based on data of potentiodynamic polarization. Efficiency inhibition decrease with increasing temperature. Adsorption mechanism which occurs is physisorption term by relying on the Frumkin isotherm equation.

### References

1. Doner, A.; Solmaz, R.; Ozcan, M.; and Gu, J. (2011). Experimental and theoretical of thiazoles as corrosion inhibitors for mild steel in sulphuric acid solution. *Corrosion Science*, 53(9), 2902-2913.
2. Abdallah, M. (2002). Rhodanineazosulpha drugs as corrosion inhibitors for corrosion of 304 stainless steel in hydrochloric acid solution. *Corrosion Science*, 44(4), 717-718.
3. EL-Etre, A.Y. (1998). Natural honey as corrosion inhibitor for metals and alloys. I. Copper in neutral aqueous solution. *Corrosion Science*, 40(11), 1845-1850.
4. Wang, J.L.; and Luo, P.H. (2003). Corrosion inhibition of zinc in phosphoric acid solution by 2-mercaptobenzimidazole. *Corrosion Science*, 45(4), 677-683.
5. Garai, S.; Garai, S.; Parasuraman, Jaisankar, S., Singh, J.K.; and Elango, A. (2012). A comprehensive study on crude ethanolic extract of *Artemisia pallens* (Asteraceae) and its active component as effective corrosion inhibitors of mild steel in acid solution. *Corrosion Science*, 60, 193-204.
6. Raja, P.B.; and Sethuraman, M.G. (2008). Natural products as corrosion inhibitor for metals incorrosive media - A review. *Materials Letter*, 62(1), 113-116.
7. Radojčić, K.I.; Berković, S.; Kovac, J.; and Vorkapić-Furac (2008). Natural honey and black radish juice as tin corrosion inhibitors. *Corrosion Science*, 50(5), 1498-1504.

8. Roberge, P.R. (2000). *Handbook of corrosion Engineering*. New York: McGraw Hill.
9. Abboud, Y.; Abourriche, A.; Saffaj, T.; Berrada, M.; Charrouf, M.; Bennamara, A.; and Hannache, H. (2009). A novel Azo Dye, 8 Quinolinol-5-Azoantipyrine as corrosion inhibitor for mild steel in acidic media. *Corrosion Science*, 23(7), 175-189.
10. Lee, D.; Young, K.; Cheol, K.W.; and Gu, J. (2012). Effect of nitrite concentration on the corrosion behaviour of carbon steel in synthetic tap water. *Corrosion Science*, 64,105- 106.
11. Jeyaprabha, C.; Sathiyarayanan, S.; Phani, K.L.N.; and Venkatachari, G. (2005). Influence of poly(aminoquinone) on corrosion inhibition of iron in acid media. *Applied Surface Science*, 252(14), 966-975.
12. Wang, L. (2006). Inhibition of mild steel corrosion in phosphoric acid solution by triazole derivatives. *Corrosion. Science*, 48(3), 608-616.
13. Hussin, M.H.; and Kassim, M.J. (2011). Electrochemical, thermodynamic and adsorption studies of (+-) catechin hydrate as natural mild steel corrosion inhibitor in 1M HCl. *International Journal of Electrochemical Science*, 6(5),1396-1414.
14. Al-Sehaibani, H. (2000). Evaluation of extracts of henna leaves as environmentally friendly corrosion inhibitors for metals. *Material. Werkstofftech*, 31(12), 1060-1063.
15. El-Etre, A.Y.; Abdallah, M.; and El-Tantawy, Z.E. (2005). Corrosion inhibition of some metals using lawsonia extract. *Corrosion Science*, 47(2), 385-395.
16. Orubite, K.O.; and Oforka, N.C. (2004). Inhibition of the corrosion of mild steel in hydrochloric acid solutions by the extracts of leaves of *Nypa fruticans* Wurmb. *Materials Letters*, 58(11), 1768-1772.
17. El-Naggar, M.M. (2007). Corrosion inhibition of mild steel in acidic medium by some sulfa drugs compounds. *Corrosion Science*, 49(5), 2226-2236.
18. Amin, M.A.; El-Rehim, S.S.A.; El-Sherbini, E.E.F.; and Bayoumi, R.S. (2007). The inhibition of low carbon steel corrosion in hydrochloric acid solutions by succinic acid: part I. Weightloss, polarization, EIS, PZC, EDX and SEM studies. *Electrochimica. Acta*, 52(15), 3588-3600.
19. Emregü l, K.C.; and Hayvali, M. (2004). Studies on the effect of vanillin and protocatechual-dehyde on the corrosion of steel in hydrochloric acid. *Material Chemistry and Physic*, 83(2), 209-216.
20. L.Vrsalović, L.; Gudić, S.; and Kliškić, M. (2012). *Salvia officinalis* L. honey as corrosion inhibitor for CuNiFe in sodium chloride solution. *Indian Journal of Chemical Technology*, 19, 96-102.
21. El-Etre, A.Y. (1998). Natural honey as corrosion inhibitor for metals and alloys. I. Copper in neutral aqueous solution. *Corrosion Science*, 40(11),1845-1850.
22. El-Etre, A.Y.; and Abdallah, M. (2000). Natural honey as corrosion inhibitor for metals and alloys. II. C-steel in high saline water. *Corrosion Science*, 42(4), 731-738.

23. Gerengi, H.; Goksu, H.; and Slepski, P. (2014). The inhibition effect of mad honey on corrosion of 2007-type aluminium alloy in 3.5% NaCl Solution. *Materials Research*, 17(1), 255-264.
24. Gapsari, F.; Soenoko, R.; Suprpto, A.; and Suprpto, W. (2015). Bee Wax Propolis extract as eco-friendly corrosion inhibitor for 304SS in Sulfuric Acid. *International Journal of Corrosion*, Volume 2015, Article ID 567202, 10 pages.
25. Fouda, A.S.; and Hamdy Badr, A. (2013). Aqueous extract of propolis as corrosion inhibitor for carbon steel in aqueous solutions. *African Journal of Pure and Applied Chemistry*, 7(10),350-359.
26. Stupnišek-Lisac, E.; Gazivoda, A.; and Madžarac, M. (2002). Evaluation of non-toxic corrosion inhibitors for copper in sulphuric acid. *Electrochimica Acta*, 47(26), 4189-4194.
27. Awad, M.I. (2006). Eco-friendly corrosion inhibitors: inhibitive action of quinine for corrosion of low carbon steel in 1MHCl. *Journal of Applied Electrochemistry*, 36(10), 1163-1168.
28. Yan, Y.; Li, W.; Cai, L.; and Hou, B. (2008). Electrochemical and quantum chemical study of purines ascorrosion inhibitors for mild steel in 1 M HCl solution. *Electrochimica Acta*, 53(20), 5953-5960.
29. Flores-De losRíos, J.P.; Sánchez-Carrillo, M.; Nava-Dino, C.G.; Chacón-Nava, J.G.; Escobedo-Bretado, M.A.; Monreal-Romero, H.A.; Bautista-Margulis, R.G.; Neri-Flores, M.A.; and Martínez-Villafañe, A. (2015). Corrosion inhibition of mild steel using Agavoideae Extract in 1M HCl Solution. *International Journal of Electrochemical Science*, 10, 10210-10222.
30. Sangeetha, M.; Rajendran, S.; Sathiyabana, J.; Krishnaveni, A.; Shanthi, P.; Manimaran, N.; and Shyamaladevi, B. (2011). Corrosion inhibition by an aqueous extract of Phyllanthus Amarus. *Portugaliae Electrochimica Acta*, 29(6), 429-444.
31. Prabhu, D.; and Rao, P. (2013). Coriandrum sativum L. A novel green inhibitor for the corrosion inhibition of aluminium in 1.0 M phosphoric acid solution. *Journal Enviromental Chemical Engineering*, 1(4),676-683.
32. Quraiishi, M.A.; Singh, A.; Singh, V.K.; and Yadav, D.K. (2010). Green approach to corrosion inhibition of mild steel in hydrochloric acid and sulphuric acid solutions by the extract of Murraya Koenigi Leaves. *Material Chemistry and Physics*, 122(1), 114-122.
33. Oguzie, E.E.; Unaegbu, C.; Ogukwe, C.N.; Okolue, B.N.; and Onuchukwu, A.I. (2004). Inhibition of mild steel corrosion in sulphuric acid using indigo dye and synergistic halide additives. *Materials Chemistry and Physics*, 84(2), 363-368.
34. Kumpawat, V.; Grag, U.; and Tak, R.K. (2009). Corrosion inhibition of aluminium in acid media by naturally occuring plant artocarpus heterophyllus and acacia senegal. *Journal Indian.Council Chemistry*, 26(1), 82-84.
35. Satapathy, A.K.; Gunasekaran, G.; Sahoo, S.C.; Amit, K., and Rodrigues, P.V. (2009). Corrosion inhibition by Justiciendarussa plant extract in hydrochloric acid solution. *Corrosion Science*, 51(12), 2848-2856.

36. Umoren, S.A.; and Obot, I.B.; (2008). Polyvinyl pyrrolidone and polyacrylamide as corrosion inhibitors for mild steel in acidic medium. *Surface Science Letters*, 15(1), 277-286.
37. Larabi, L.; Benali, O.; and Harek, Y. (2007). Corrosion inhibition of cold rolled steel in 1M HClO<sub>4</sub> solutions by N-naphtylNO-phenylthiourea. *Materials Letters*, 61(14), 3287-3291.
38. Umoren, S.A.; Obota, I.B.; Ebensob, E.E.; and Obi-Egbedib, N.O. (2009). The Inhibition of aluminium corrosion in hydrochloric acid solution by exudate gum from *Raphia hookeri*. *Desalination*, 247(1), 561-572.